

# Mechanisms of Spontaneous Current Generation in an Inhomogeneous $d$ -Wave Superconductor

M.H.S. Amin<sup>a</sup>, A.N. Omelyanchouk<sup>b</sup>, and A.M. Zagoskin<sup>a,c</sup>

<sup>a</sup>*D-Wave Systems Inc., 320-1985 W. Broadway, Vancouver, B.C., V6J 4Y3, Canada*

<sup>b</sup>*B.I. Verkin Institute for Low Temperature Physics and Engineering,*

*Ukrainian National Academy of Sciences, Lenin Ave. 47, Kharkov 310164, Ukraine*

<sup>c</sup>*Physics and Astronomy Dept., The University of British Columbia,*

*6224 Agricultural Rd., Vancouver, B.C., V6T 1Z1, Canada.*

A boundary between two  $d$ -wave superconductors or an  $s$ -wave and a  $d$ -wave superconductor generally breaks time-reversal symmetry and can generate spontaneous currents due to proximity effect. On the other hand, surfaces and interfaces in  $d$ -wave superconductors can produce localized current-carrying states by supporting the  $\mathcal{T}$ -breaking combination of dominant and subdominant order parameters. We investigate spontaneous currents in the presence of both mechanisms and show that at low temperature, counter-intuitively, the subdominant coupling *decreases* the amplitude of the spontaneous current due to proximity effect. Superscreening of spontaneous currents is demonstrated to be present in any  $d$ - $d$  (but not  $s$ - $d$ ) junction and surface with  $d + id'$  order parameter symmetry. We show that this superscreening is the result of contributions from the local magnetic moment of the condensate to the spontaneous current.

(February 1, 2008)

The time-reversal symmetry ( $\mathcal{T}$ ) breaking on surfaces and interfaces of superconductors with  $d$ -wave orbital pairing has been intensively investigated in the last years both in theory and experiment [1–8]. Several mechanisms of  $\mathcal{T}$ -breaking have been proposed, which fall in two categories: appearance of subdominant order parameter and proximity effect [2,3].

In the first case the surface or interface suppresses the dominant order parameter ( $d_{x^2-y^2}$  in YBCO [4]). If the pairing interaction in other channels is nonzero, the subdominant order parameter will be formed below the corresponding, smaller critical temperature  $T_{c2}$  [9]. The combination of the two order parameters with complex coefficients breaks the  $\mathcal{T}$ -symmetry [1] and leads to spontaneous surface currents and magnetic fluxes. Usually  $d_{x^2-y^2} \pm is$  or  $d_{x^2-y^2} \pm id_{xy}$  combinations are predicted. Recent observations of zero bias peak splitting in surface tunneling experiments [5] and spontaneous fractional flux (0.1-0.2  $\Phi_0$ ) near the “green phase” inclusions in YBCO films [6] agree with this picture.

The other possibility arises in a junction between two  $d$ -wave superconductors with different orientations of the order parameter [7]. In this case the two order parameters necessary to form a  $\mathcal{T}$ -breaking state,  $d_{1,2}$ , are supplied by the bulk superconductors. The equilibrium phase difference across the boundary,  $\phi_0$ , is generally neither 0 nor  $\pi$ , and therefore the states with  $d_1 + e^{\pm i\phi_0} d_2$  orderings are degenerate and may support spontaneous currents. The same mechanism applies in case of a boundary between an  $s$ - and a  $d$ -wave superconductor [8].

In order to investigate the interplay of both mechanisms, in this letter we consider  $d$ - $d$  and  $s$ - $d$  interfaces as well as (110)-surface of a  $d$ -wave superconductor. We will see that generally the spontaneous currents due to proximity effect are suppressed by the existence of subdominant order parameter. There is also an important

distinction between the  $d$ - $d$  and  $s$ - $d$  cases: In the former case the superconductor may have local orbital and magnetic moments, contributing to the non-dissipative current. In the latter case such a contribution is absent. Our results indicate that in a clean  $d$ - $d$  junction all of the spontaneous current can be attributed to this “molecular currents” mechanism. We also show that this effect leads to “superscreening” of spontaneous currents in  $d$ - $d$  junctions (i.e. to the existence of counter-currents independent of the Meissner effect).

We use the standard approach based on quasiclassical Eilenberger equations for Green’s functions integrated over energy [10]

$$\mathbf{v}_F \cdot \nabla \hat{G}_\omega + [\omega \hat{\tau}_3 + \hat{\Delta}, \hat{G}_\omega] = 0, \quad (1)$$

where  $\omega$  is the Matsubara frequency and

$$\hat{G}_\omega(\mathbf{v}_F, \mathbf{r}) = \begin{pmatrix} g_\omega & f_\omega \\ f_\omega^\dagger & -g_\omega \end{pmatrix}, \quad \hat{\Delta}(\mathbf{v}_F, \mathbf{r}) = \begin{pmatrix} 0 & \Delta \\ \Delta^\dagger & 0 \end{pmatrix}.$$

Here  $\hat{G}_\omega$  is the matrix Green’s function and  $\Delta$  is the superconducting order parameter. They both are functions of Fermi velocity  $\mathbf{v}_F$  and position  $\mathbf{r}$ . We also need to satisfy the normalization condition  $g_\omega = \sqrt{1 - f_\omega f_\omega^\dagger}$ . In general case  $\Delta$  depends on the direction of the vector  $\mathbf{v}_F$  and is determined by the self-consistency equation

$$\Delta(\mathbf{v}_F, \mathbf{r}) = 2\pi N(0)T \sum_{\omega>0} < V_{\mathbf{v}_F \mathbf{v}_F'} f_\omega(\mathbf{v}_F', \mathbf{r}) >_\theta, \quad (2)$$

where  $V_{\mathbf{v}_F \mathbf{v}_F'}$  is the interaction potential. In our calculations we will consider two-dimensional case;  $N(0) = \frac{m}{2\pi}$  is 2D density of states and  $< \dots >_\theta = \int_0^{2\pi} \frac{d\theta}{2\pi} \dots$  is the averaging over directions of 2D vector  $\mathbf{v}_F = (v_F \cos \theta, v_F \sin \theta)$ .

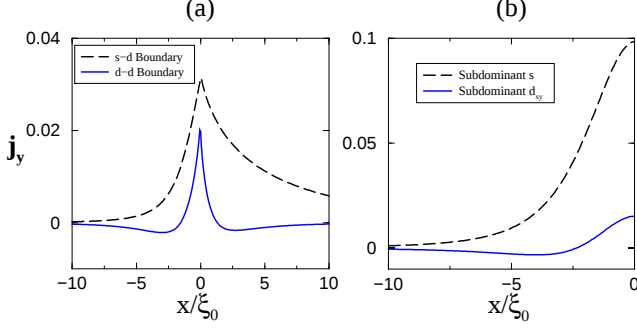


FIG. 1. (a) Spontaneous current for  $d$ - $d$  and  $s$ - $d$  junctions. The boundary is located at  $x = 0$ . Calculations are done at  $t \equiv T/T_c = 0.05$ , with  $T_{c2} = 0.05T_c$  for the  $d$ - $d$  case and  $T_{cs} = 0.1T_c$  and  $T_{c2} = 0.05T_c$  for the  $s$ - $d$  junction. (b) Spontaneous current at the (110)-surface of a  $d$ -wave superconductor at  $t = 0.05$  with  $T_{c2} = T_{cs} = 0.1T_c$  for both  $s$  or  $d_{xy}$  subdominant order parameters.

In general it is possible to obtain a mixture of different symmetries of the order parameter,  $\Delta(\theta) = \Delta_{x^2-y^2}(\theta) + \Delta_{xy}(\theta) + \Delta_s$  where  $\Delta_{x^2-y^2}(\theta) = \Delta_1 \cos 2\theta$ ,  $\Delta_{xy}(\theta) = \Delta_2 \sin 2\theta$  and  $\Delta_s$  are the  $d_{x^2-y^2}$ ,  $d_{xy}$ , and the  $s$ -wave components of the order parameter respectively. The corresponding interaction potential,  $V_{\theta\theta'} = V_{d1} \cos 2\theta \cos 2\theta' + V_{d2} \sin 2\theta \sin 2\theta' + V_s$ , must be substituted in the self-consistency equation (2) for the order parameter in each channel. The current density  $\mathbf{j}(\mathbf{r})$  is found from the solution of the matrix equation (1) as

$$\mathbf{j}(\mathbf{r}) = -4\pi e N(0) T \sum_{\omega > 0} \langle \mathbf{v}_F g_{\omega}(\mathbf{v}_F, \mathbf{r}) \rangle_{\theta}. \quad (3)$$

Here we consider three cases, (i) boundary between two semi-infinite  $d$ -wave superconductors with crystallographic orientations with respect to the boundary given by angles  $\chi_l$  and  $\chi_r$  (“ $d$ - $d$  interface”), (ii) boundary between an  $s$ -wave and a  $d$ -wave superconductor with  $45^\circ$  orientation (“ $45^\circ$   $s$ - $d$  interface”), and (iii) (110)-surface of a  $d$ -wave superconductor. In all three cases it is possible to have time reversal symmetry breaking ground state. The direction and magnitude of the spontaneous current depends on the relative phases of the order parameters.

Assuming constant order parameters on both sides of an interface, one can obtain an analytical (non-selfconsistent) expression for the current density

$$\mathbf{j}(x) = 4\pi e N(0) T \sin \phi \sum_{\omega > 0} \left\langle \frac{\mathbf{v}_F \Delta_l \Delta_r \text{sign}(\cos \theta)}{\Omega_l \Omega_r + \omega^2 + \Delta_l \Delta_r \cos \phi} e^{-2|x|\Omega_r/|v_F \cos \theta|} \right\rangle_{\theta}, \quad (4)$$

where  $l$  ( $r$ ) labels left (right) side of the interface, and  $\Omega_i = \sqrt{\omega^2 + |\Delta_i|^2}$ . This expression is valid for arbitrary symmetry of the order parameters  $\Delta_{l,r}$ . For a  $d$ - $d$  interface we have  $\Delta_l = \Delta_0(T) \cos 2(\theta - \chi_l)$  and  $\Delta_r = \Delta_0(T) \cos 2(\theta - \chi_r)$ , where  $\Delta_0(T)$  depends on the superconducting coupling and temperature.

Our numerical calculations were based on Schopohl-Maki parameterization of Green’s functions [11],

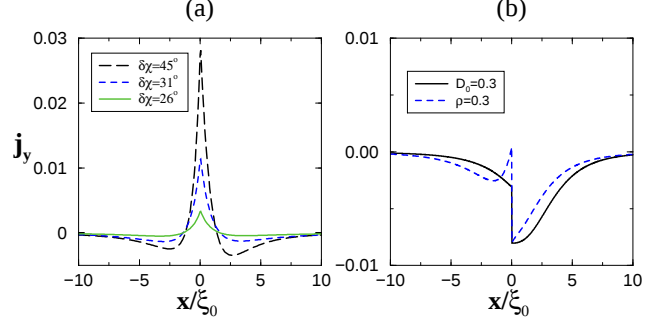


FIG. 2. (a) Spontaneous currents for  $(0^\circ - \delta\chi)$  junctions with different misorientation angles. (b) Spontaneous current at imperfect  $(0^\circ - 45^\circ)$  junctions. Solid line: junction with transparency  $D_0 = 0.3$ . Dashed line: junction with roughness  $\rho = 0.3$ . All calculations are done at  $t = 0.1$ .

$$g = \frac{1 - aa^\dagger}{1 + aa^\dagger}, \quad f = \frac{2a}{1 + aa^\dagger}, \quad f^\dagger = \frac{2a^\dagger}{1 + aa^\dagger},$$

which transforms Eq. (1) into

$$\mathbf{v}_F \cdot \nabla a = 2\omega a - \Delta^* a^2 + \Delta \quad (5)$$

$$-\mathbf{v}_F \cdot \nabla a^\dagger = 2\omega a^\dagger - \Delta a^{\dagger 2} + \Delta^*. \quad (6)$$

For positive  $v_x$ , Eq. (5) (Eq. (6)) is stable if the boundary condition at  $x \rightarrow -\infty$  ( $+\infty$ ) is chosen. The opposite is true for negative  $v_x$ . We use the solutions in a homogeneous system,  $a = \Delta/(\omega + \Omega)$  and  $a^\dagger = \Delta^*/(\omega + \Omega)$  as boundary conditions at  $\pm\infty$ . The values of  $a$  ( $a^\dagger$ ) at all other points on the trajectory are then easily found. The self-consistency is introduced through iterations, assuming a constant order parameter in either half of the junction for the first iteration.

Fig. 1a shows the spatial distribution of the spontaneous current in  $d$ - $d$  and  $s$ - $d$  junctions. The left superconductor is a  $d$ -wave superconductor with  $45^\circ$  crystal orientation with respect to the boundary. The right side is either an  $s$ -wave or a  $d$ -wave superconductor aligned with the boundary. The current distribution is qualitatively different in  $s$ - $d$  and  $d$ - $d$  junctions. In the  $d$ - $d$  case, the current density is at maximum in a layer of width of about coherence length,  $\xi_0 = v_F/\pi\Delta$ , along the boundary; there also exists a counter-flow, spread over about  $10\xi_0$  on either side of the boundary. The total current in  $y$ -direction is zero within the numerical accuracy, *independently* on the right and left sides of the junction. This effect can be called “superscreening”, since the resulting magnetic field of the spontaneous current is cancelled on the scale of  $\sim 10\xi_0 \ll \lambda_L, \lambda_J$ , the London and Josephson magnetic penetration depths. Note that this has nothing to do with the Meissner screening; it appears without taking into account the vector potential of the magnetic field of the current (and makes it unnecessary) [12]. On the contrary, in the  $s$ - $d$  junction the counter-flows are absent (unless the Meissner effect is taken into account [8]).

The same situation takes place near the surface, *if* the subdominant pairing is present. Fig. 1b shows the cur-

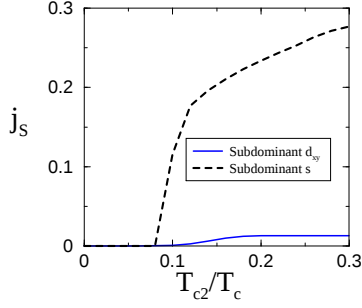


FIG. 3. The effect of subdominant interaction on the spontaneous current  $j_S$  ( $\equiv j_y(x=0)$ ) at the surface of a  $d$  wave superconductor. A second order phase transition happens at  $T_{c2} = T = 0.1T_c$

rent distribution at the (110)-surface of a  $d$ -wave superconductor. If  $d_{xy}$  is the leading subdominant order parameter, the form of the current distribution is similar to the one in the  $d$ - $d$  boundary. The superscreening is absent if the subdominant order parameter is  $s$ -wave.

The superscreening effect can be obtained analytically from the non-selfconsistent expression (4) in case of 0-45° junction. The nullification of the total current results from integrating the spontaneous current

$$\int_0^\infty dx j_y(x) \propto \left\langle \frac{\Delta_l \Delta_r \sin \theta \operatorname{sign}(\cos \theta)}{\Omega_l \Omega_r + \omega^2 + \Delta_l \Delta_r \cos \phi} \frac{v_F |\cos \theta|}{\Omega_r} \right\rangle_\theta \sin \phi$$

which is zero after angle averaging. Our numerical calculations however show that in clean boundary junctions the total current is zero (within the numerical accuracy) even after self-consistent calculation and at all other misorientation angles (see Fig. 2a).

To understand the situation, let us recall that in a system with local magnetic moment density  $\mathbf{m}(\mathbf{r})$  the “molecular currents” flow with density  $\mathbf{j}(\mathbf{r}) = c \nabla \times \mathbf{m}(\mathbf{r})$ . In a superconductor with order parameter  $d_{x^2-y^2} + e^{i\phi_0} d_{xy}$  local orbital/magnetic moment density

$$\begin{aligned} \mathbf{m}(\mathbf{r}) &\propto \hat{\mathbf{z}} \int_0^{2\pi} \frac{d\theta}{2\pi} (\Delta_1(x) \cos 2\theta + \Delta_2(x) e^{-i\phi_0} \sin 2\theta) \\ &\quad \times \frac{1}{i} \frac{\partial}{\partial \theta} (\Delta_1(x) \cos 2\theta + \Delta_2(x) e^{i\phi_0} \sin 2\theta) \\ &= 2\Delta_1(x)\Delta_2(x)\hat{\mathbf{z}} \sin \phi_0. \end{aligned}$$

The contribution to the spontaneous current is thus  $\mathbf{j}(\mathbf{r}) \propto \nabla \times \mathbf{m}(\mathbf{r}) \parallel \hat{\mathbf{y}}$ . Notice that the same expression is obtained from the Ginzburg-Landau equations [13] ( $\mathbf{j} \propto \nabla \times (\hat{\mathbf{z}} \operatorname{Im} d_1(\mathbf{r}) d_2^*(\mathbf{r}))$ ). The total current in  $y$ -direction due to this mechanism is  $I_{\text{total}} \propto \int_\Omega d\mathbf{S} \cdot \nabla \times \mathbf{m} = \oint_{\partial\Omega} d\mathbf{l} \cdot \mathbf{m} = 0$ , where  $\Omega$  is a cross section perpendicular to the junction from  $x = -\infty$  to  $\infty$  and  $\partial\Omega$  is its boundary. The latter integral is obviously zero because  $d\mathbf{l} \cdot \mathbf{m} = 0$  ( $\mathbf{m} \parallel \hat{\mathbf{z}}$ ) everywhere except where the contour closes ( $x = \pm\infty$ ), but there  $\mathbf{m} = 0$ . This is certainly not the case in  $s$ - $d$  junctions (cf. Fig. 1). (Of course, since

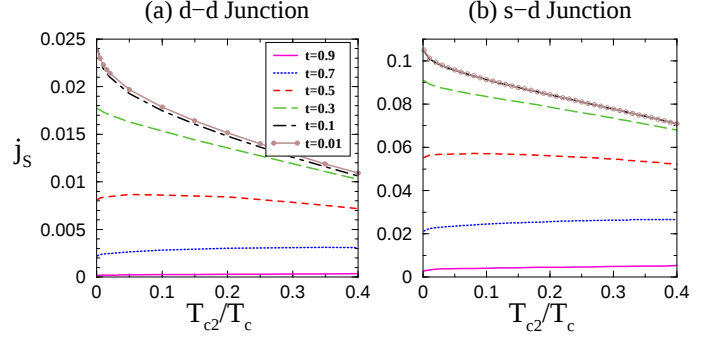


FIG. 4. Suppression of spontaneous current by subdominant order parameter. (a) A  $d$ - $d$  grain boundary. (b) An  $s$ - $d$  interface. In the  $s$ - $d$  case, we have taken the same  $T_c$  for both sides and also  $T_{cs} = T_{c2}$ .

the Meissner currents must be taken into account in this case, the results presented in Fig. 1 are valid only if the system size is much less than the London penetration depth.)

We also calculate the spontaneous current for an imperfect boundary, i.e a boundary with arbitrary transparency  $D_0$  and also with finite roughness  $\rho$ . We use Zaitsev’s boundary condition [14,15] to incorporate the finite transparency effect. For surface roughness we assume a thin layer with scattering centers at the junction [16]. We take the mean free path  $l$  and the layer thickness  $d$  to zero while keeping  $\rho \equiv d/l$  finite. The details of calculations will be given in a separate publication. Here we only present the results of our calculation for asymmetric (0°-45°)  $d$ - $d$  junction in Fig. 2b. As is clearly seen, the spontaneous currents now does not necessarily have a counterflow (at small  $\rho$  or  $D_0 \approx 1$  there will be some counterflow), and the exact superscreening no longer takes place. They are now carried merely by Andreev bound states at the interface, the same as in  $s$ - $d$  or SND [8] junctions. Although near realistic surfaces/interfaces with  $d$ - $d$  ordering the superscreening is not complete, the magnetic fields created by the spontaneous currents are nevertheless suppressed on very short distances. This can be practically important for attempting to build a “quiet” qubit based on such junctions [17].

Fig. 3 presents the spontaneous current as a function of the subdominant critical temperature  $T_{c2}$  at the (110)-surface of a  $d$ -wave superconductor. One notices that the spontaneous current vanishes when  $T_{c2} < T$ . In fact, at temperatures below  $T = T_{c2}$  the subdominant order parameter starts to appear at the surface through a second-order phase transition. Spontaneous symmetry breaking and generation of the spontaneous current are the consequences of the emergence of this second order parameter. The symmetry of the subdominant order parameter is dictated by whichever channel ( $s$  or  $d_{xy}$ ) has stronger interaction potential.

In the  $d$ - $d$  and  $s$ - $d$  interfaces on the other hand, the subdominant order parameter is induced by the proximity to a different superconductor. One important difference is

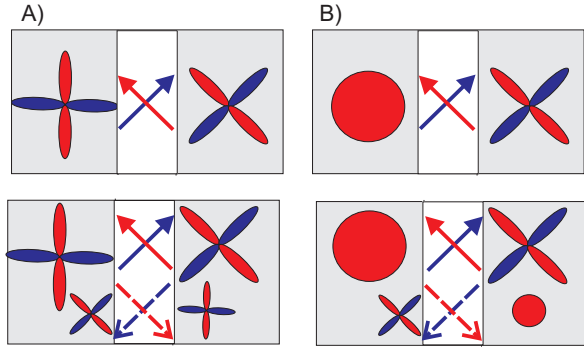


FIG. 5. The DND and SND model of a  $\mathcal{T}$ -breaking junction. (a) DND junction. The normal region contains current-carrying Andreev bound states (arrows); in equilibrium net current across the boundary is zero, while the spontaneous currents flow along the normal layer (above). If subdominant order parameter is present, the additional set of Andreev levels in equilibrium carries spontaneous current in the opposite direction (below). The model gives the same predictions for SND case (b).

that unlike the surface case, at the  $d$ - $d$  or  $s$ - $d$  interfaces the presence of the subdominant order parameter is not necessary for generation of spontaneous current. From Eqs. (3) and (1) we see that it is the Green's function (the pairing *amplitude*), not the order parameter (pairing *potential*), which determines the current. In fact, the presence of subdominant order parameter does not always increase the spontaneous current. At low temperatures, it actually *decreases* the spontaneous current [18]. This counter-intuitive effect is displayed in Fig. 4 in which the spontaneous current is plotted as a function of  $T_{c2}$ . The temperature used in the calculations is  $t = 0.1$  and we take the same  $T_c$  for both  $d$  and  $s$ -wave superconductors. Increasing  $T_{c2}$  increases the interaction in the subdominant channel and therefore the magnitude of the subdominant order parameter. The spontaneous current on the other hand decreases with increasing  $T_{c2}$ . The situation is the same for both  $d$ - $d$  and  $s$ - $d$  interfaces.

The decrease of the spontaneous currents when there is interaction in the subdominant channel may seem paradoxical. Nevertheless it is easy to understand in the DND-model of  $\mathcal{T}$ -breaking junction. [8,19] (Fig. 5). First consider the case without subdominant order parameters. The spontaneous currents in this model flow exclusively within the normal layer and are carried by “zero” and “ $\pi$ ”- Andreev bound states, which connect the lobes of  $d$ -wave order parameter with the same and opposite signs respectively: in equilibrium there is no net current across the boundary. Now let us assume that the subdominant order parameters are present. Due to continuity, they must have the same phase as the dominant order parameter on the other side (Fig. 5). Therefore now we will have two extra sets of current-carrying Andreev states, the ones linking the *subdominant* order parameters, and it is obvious that the spontaneous currents they carry will always flow opposite to the currents carried by the “dominant-dominant” states.

In conclusion, we have investigated the spontaneous currents near the surface and  $d$ - $d$  and  $s$ - $d$  boundaries in  $d$ -wave superconductors. We obtained the contributions to the spontaneous currents due to the proximity effect and due to the subdominant order parameter generation, and found that at interfaces the latter generally decreases the magnitude of the effect. In  $d$ - $d$  junctions, we separated the contribution from the local orbital/magnetic moment of the condensate; this contribution dominates spontaneous currents in clean  $d$ - $d$  junctions, which explains the superscreening of the spontaneous currents in such systems.

We would like to thank S. Rashkeev, G. Rose, A. Smirnov and I. Herbut for helpful discussions.

- 
- [1] M. Sigrist, Progr. Theor. Phys. **99**, 899 (1998).
  - [2] M. Fogelström and S.-K. Yip, Physical Review B **57**, R14060 (1998).
  - [3] T. Löfwander, V.S. Shumeiko, and G. Wendin, preprint (cond-mat/0008235).
  - [4] I. Iguchi et al., Phys. Rev. B **62**, R6131 (2000).
  - [5] M. Covington et al., Phys. Rev. Letters **79**, 277 (1997); L.H. Greene et al., Physica B **280**, **159** (2000).
  - [6] F. Tafuri and J.R. Kirtley, preprint (cond-mat/0003106).
  - [7] S. Yip, J. Low Temp. Phys. **91** 203 (1993); T.P. Devreux and P. Fulde, Phys. Rev. B **47**, 14 638 (1993); Y. Tanaka, Phys. Rev. Letters **72**, 3871 (1994).
  - [8] A. Huck, A. van Otterlo, and M. Sigrist, Phys. Rev. B **56**, 14 163 (1997).
  - [9] E.M. Lifshits and L.P. Pitaevskii, Statistical physics, p.2 (Teoreticheskaya fizika, v.IX). Oxford ; New York : Pergamon Press (1980); §54.
  - [10] G. Eilenberger, Z. Phys. **214** 195 (1968).
  - [11] N. Schopohl and K. Maki, Phys. Rev. B **52**, 490 (1995); N. Schopohl, preprint (cond-mat/9804064).
  - [12] A similar distribution of spontaneous current density on (110) surfaces and interfaces of  $d$ -superconductors was obtained in [2] (Fig.4a).
  - [13] D.B. Bailey, M. Sigrist and R.B. Laughlin Phys. Rev. B **55**, 15239, (1997).
  - [14] A.V. Zaitsev, JETP **59** 1015 (1984).
  - [15] S.-K. Yip, J. Low Temp. Phys. **109** 547 (1997).
  - [16] F.J. Gulletto, G. Keiselmann, and D. Rainer, in *Proceedings of the 17th International Conference on Low Temperature Physics*, (North Holland, Amsterdam, 1984) p.1027; A.A. Golubov, and M. Yu. Kupriyanov, preprint (cond-mat/9901318).
  - [17] L.B. Ioffe et al. Nature **398**, 679 (1999).
  - [18] Subdominant pairing potential also suppresses the Josephson current. See Y. Tanaka and S. Kashiwaya Phys. Rev. B **58**, 2948 (1998)
  - [19] A.M. Zagorin, J.Phys.: Cond. Matter **9**, L419 (1997).